

lecture
twenty one


steel construction
bolts, welds & light gages




nmmc.org

Connections

- needed to:
 - support beams by columns
 - connect truss members
 - splice beams or columns
- transfer load
- subjected to
 - tension or compression
 - shear
 - bending




(a) Framed beam (shear) connection.
 $e = \text{Eccentricity}; M = P \times e$



(b) Moment connection (rigid frame).
 $M = \text{Moment due to beam bending}$

Bolts


- bolted steel connections

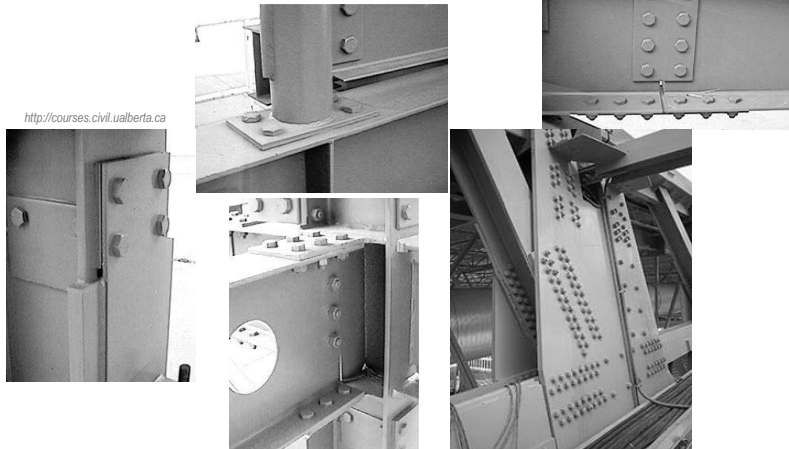

<http://courses.civil.ualberta.ca>

Welds

- welded steel connections

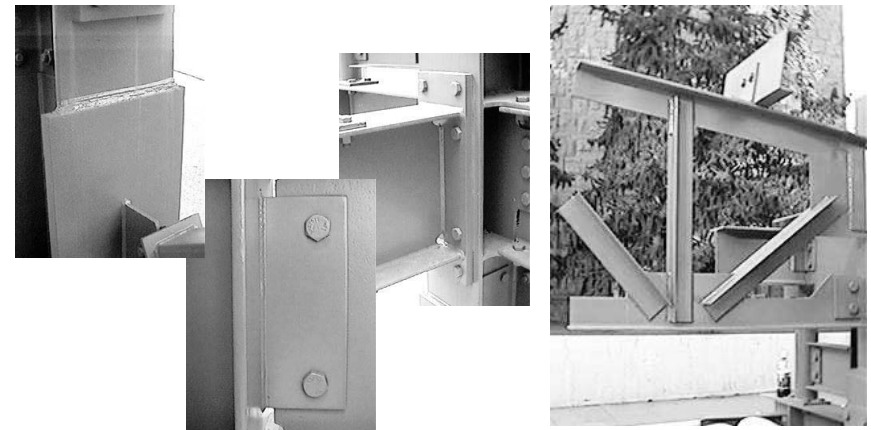

<http://courses.civil.ualberta.ca>

Bolts

- types

- materials


- high strength
- A307, A325, A490

- location of threads

- included - N
- excluded - X

- friction or bearing (SC)

- always tightened

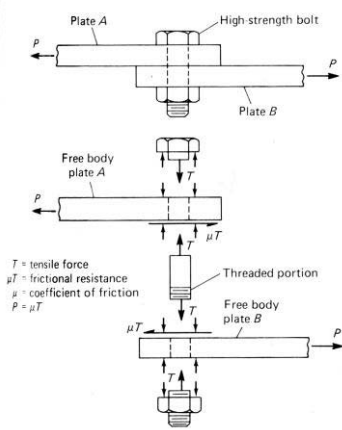

Bolted Connection Design

- considerations

- bearing stress



- yielding

- shear stress

- single & double

- member

- rupture

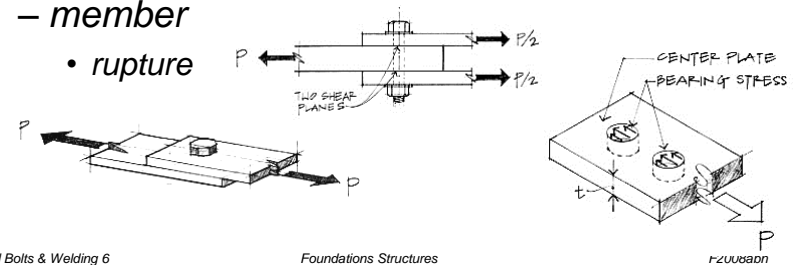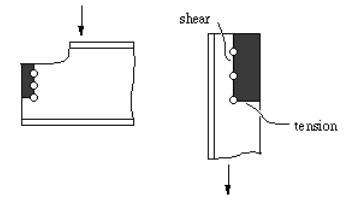

Bolts

- rarely fail in bearing

- holes considered 1/8" larger

- shear & tension

$$R_a \leq \frac{R_n}{\Omega} \quad R_u \leq \phi_v R_n$$

$$\phi_v = 0.75$$

- single shear or tension

$$R_n = F_n A_b$$

- double shear

$$R_n = F_n 2A_b$$


Bolts

Table 7-1
Available Shear Strength of Bolts, kips

Nominal Bolt Diameter, d, in.		3/8		1/2		3/4		1			
Nominal Bolt Area, in. ²		0.307		0.442		0.601		0.785			
ASTM Desig.	Thread Cond.	F _u /k (ksi)		F _y /k (ksi)		F _u /k (ksi)		F _y /k (ksi)			
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD		
Group A	N	27.0	40.5	S 8.29	12.4	11.9	17.9	16.2	24.3	21.2	31.8
	D	19.6	29.4	29.9	35.8	32.5	49.7	42.4	63.6		
Group B	N	34.0	51.0	S 10.4	15.7	15.0	22.5	20.4	30.7	26.7	40.0
	D	20.9	31.3	30.1	45.1	40.9	61.5	53.4	80.1		
Group B	N	34.0	51.0	S 10.4	15.7	15.0	22.5	20.4	30.7	26.7	40.0
	D	20.9	31.3	30.1	45.1	40.9	61.5	53.4	80.1		
A307	N	34.0	51.0	S 12.9	19.3	18.6	27.8	25.2	37.9	33.0	49.5
	D	25.8	38.7	37.1	55.7	50.5	75.7	65.9	98.9		
A307	N	13.5	20.3	S 4.14	6.23	5.97	8.97	8.11	12.2	10.8	15.8
	D	8.29	12.5	11.8	17.9	16.2	24.4	21.2	31.8		

Table 7-2
Available Tensile Strength of Bolts, kips

Nominal Bolt Diameter, d, in.		3/8		1/2		3/4		1			
Nominal Bolt Area, in. ²		0.307		0.442		0.601		0.785			
ASTM Desig.	Thread Cond.	F _u /k (ksi)		F _y /k (ksi)		F _u /k (ksi)		F _y /k (ksi)			
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD		
Group A	N	45.0	67.5	13.8	20.7	18.9	28.8	22.1	40.6	36.3	53.0
	D	58.5	87.8	17.3	26.0	25.0	37.4	34.0	61.0	44.4	66.6
Group B	N	22.5	33.8	6.90	10.4	9.94	14.9	13.5	20.3	17.7	26.5
	D	14.5	21.8	4.45	6.55	4.97	7.45	5.33	7.85	6.90	10.1
A307	N	45.0	67.5	13.8	20.7	18.9	28.8	22.1	40.6	36.3	53.0
	D	58.5	87.8	17.3	26.0	25.0	37.4	34.0	61.0	44.4	66.6
A307	N	13.5	20.3	3.93	5.90	4.14	6.23	4.59	6.88	6.18	9.00
	D	8.29	12.5	5.08	7.62	5.39	8.08	5.74	8.61	7.68	11.2



Bolts

- bearing

$$R_a \leq \frac{R_n}{\Omega} \quad R_u \leq \phi R_n$$

$$\phi = 0.75$$

– deformation is concern

$$R_n = 1.2L_c t F_u \leq 2.4dt F_u$$

– deformation isn't concern

$$R_n = 1.5L_c t F_u \leq 3.0dt F_u$$

– long slotted holes

$$R_n = 1.0L_c t F_u \leq 2.0dt F_u$$

L_c – clear length to edge or next hole (ex. 1 1/4", 3")

Bolts

Table 7-5
Available Bearing Strength at Bolt Holes Based on Edge Distance
Kips/in. thickness

Hole Type	Edge Distance L_e , in.	F_u , ksi	Nominal Bolt Diameter, d , in.								
			5/8		3/4		7/8		1		
			ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD	
STD	1 1/4	58	31.5	47.3	29.4	44.0	27.2	40.8	25.0	37.2	
			35.3	53.0	32.9	49.4	30.5	45.7	28.0	42.0	
			43.5	65.3	52.2	78.3	53.3	79.9	51.1	76.7	
SSLT	2	58	48.6	73.1	58.5	87.8	59.7	89.6	57.9	85.6	
			58	28.3	42.4	26.1	39.2	23.9	35.9	20.7	31.0
			65	31.7	47.5	29.3	43.9	28.8	40.2	23.2	34.7
SSLP	1 1/4	58	43.5	65.3	52.2	78.3	50.0	75.0	46.8	70.1	
			48.6	73.1	58.5	87.8	56.1	84.1	52.4	78.6	
			58	29.4	44.0	27.2	40.8	25.0	37.5	21.8	32.6
OVS	2	58	43.5	65.3	52.2	78.3	51.1	76.7	47.9	71.8	
			48.6	73.1	58.5	87.8	57.3	85.9	53.6	80.4	
			58	18.3	24.5	10.9	16.3	5.44	8.16	—	—
LSLP	1 1/4	58	18.3	27.4	12.2	18.3	6.09	9.14	—	—	
			42.4	63.8	37.0	55.5	37.5	47.3	28.1	39.2	
			47.5	71.3	41.4	62.2	35.3	53.0	29.3	43.9	
LSLT	2	58	26.3	39.4	24.5	36.7	22.7	34.0	20.9	31.3	
			29.5	44.2	27.4	41.1	26.4	38.1	23.4	35.6	
			36.3	54.4	43.5	65.3	44.4	66.6	42.6	63.9	
STD, SSLT, SSLP, OVS, LSLP	1 1/4	58	43.5	65.3	52.2	78.3	60.9	91.4	69.6	104	
			48.6	73.1	58.5	87.8	68.3	102	78.0	117	
			58	36.3	54.4	43.5	65.3	50.8	76.1	58.0	87.0
LSLT	2	58	36.3	54.4	43.5	65.3	50.8	76.1	58.0	87.0	
			48.6	60.9	48.8	73.1	58.9	85.3	65.0	97.6	
			58	17.5	24.5	10.9	16.3	5.44	8.16	—	—
Edge distance for full bearing strength $L_e \geq 4d$, in.	SSLT, LSLT	1 1/4	2	2	2	2	2	2	2		
			1 1/2	2	2	2	2	2	2		
			2	2	2	2	2	2	2		
Edge distance for full bearing strength $L_e \geq 4d$, in.	OVS, LSLP	1 1/4	2	2	2	2	2	2	2		
			1 1/2	2	2	2	2	2	2		
			2	2	2	2	2	2	2		



Table 7-3 (continued)
Slip-Critical Connections Available Shear Strength, kips (Class A Faying Surface, $\mu = 0.30$)

Hole Type	Loading	Nominal Bolt Diameter, d , in.							
		5/8		3/4		7/8		1	
		Minimum Group B Bolt Pretension, kips							
		24	35	49	64				
STD/SSLT	S	5.42	8.14	7.01	11.9	11.1	16.6	14.5	21.7
		10.8	16.3	15.8	23.7	22.1	33.2	28.9	43.4
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD
OVS/SSLP	S	4.82	6.92	6.74	10.1	9.44	14.1	12.3	18.4
		9.25	13.8	13.5	20.2	18.9	28.2	24.7	36.9
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD
LSL	D	3.80	5.70	5.54	8.31	7.76	11.6	10.1	15.2
		7.60	11.4	11.1	16.6	15.5	23.3	20.3	30.4
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD
Hole Type	Loading	Nominal Bolt Diameter, d , in.							
		1 1/4		1 1/2		1 3/4		2	
		Minimum Group B Bolt Pretension, kips							
		80	102	121	148				
STD/SSLT	S	18.1	27.1	23.1	34.6	27.3	41.0	33.4	50.2
		36.2	54.2	46.1	69.2	54.7	82.0	66.9	100
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD
OVS/SSLP	S	15.4	23.1	19.6	29.4	23.3	34.9	28.5	42.6
		30.8	46.1	39.3	58.8	46.6	69.7	57.0	85.3
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD
LSL	D	12.7	19.0	16.2	24.2	19.2	28.7	23.4	35.1
		25.3	38.0	32.3	48.4	38.3	57.4	46.9	70.2
		ASD	LFRD	ASD	LFRD	ASD	LFRD	ASD	LFRD

Welded Connection Design

- considerations

- shear stress
- yielding
- rupture

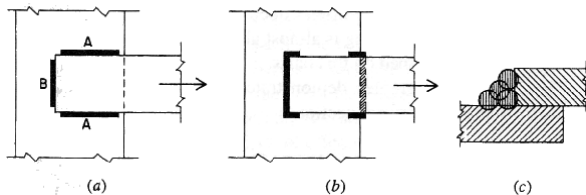


Welded Connection Design

- weld terms

- butt weld
- fillet weld
- plug weld
- throat



- field welding
- shop welding

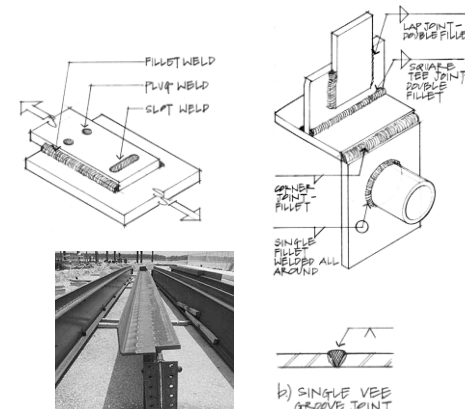

(AISC - Steel Structures of the Everyday)

Welded Connection Design

- weld process
 - melting of material
 - melted filler - electrode
 - shielding gas / flux
 - potential defects
- weld materials
 - E60XX
 - E70XX
 - $F_{EXX} = 70 \text{ ksi}$

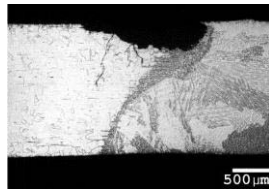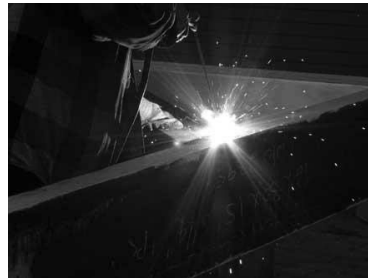


Steel Bolts & Welding 13
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Welded Connection Design

- shear failure assumed
- throat
 - $T = 0.707 \times \text{weld size}$
- area
 - $A = T \times \text{length of weld}$
- weld metal generally stronger than base metal (ex. $F_y = 50 \text{ ksi}$)

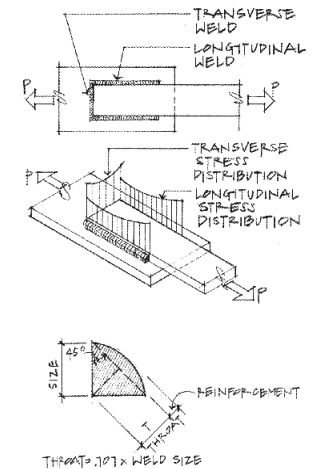


Steel Bolts & Welding 14
Lecture 18

Foundations Structures
ARCH 331

Su2011abn

Welded Connection Design

- minimum
 - table
- maximum
 - material thickness (to 1/4")
 - 1/16" less
- min. length
 - 4 x size min.
 - $\geq 1 \frac{1}{2}$ "



Material Thickness of Thicker Part Joined, in. (mm)	Minimum Size of Fillet Weld ^[a] in. (mm)
To 1/4 (6) inclusive	1/8 (3)
Over 1/4 (6) to 1/2 (13)	3/16 (5)
Over 1/2 (13) to 3/4 (19)	1/4 (6)
Over 3/4 (19)	5/16 (8)

[a] Leg dimension of fillet welds. Single pass welds must be used.
[b] See Section J2.2c for maximum size of fillet welds.

Steel Bolts & Welding 15
Lecture 18

Foundations Structures
ARCH 331

Su2011abn

Welded Connection Design

- shear

$$R_a \leq \frac{R_n}{\Omega} \quad R_u \leq \phi R_n$$

$$\phi = 0.75$$

$$R_n = 0.6 F_{EXX} \underbrace{Tl}_{\text{area}} = Sl$$

– table for ϕS

Weld Size (in.)	E60XX (k/in.)	E70XX (k/in.)
3/16	3.58	4.18
1/4	4.77	5.57
5/16	5.97	6.96
3/8	7.16	8.35
7/16	8.35	9.74
1/2	9.55	11.14
5/8	11.93	13.92
3/4	14.32	16.70

(not considering increase in throat with submerged arc weld process)



Steel Bolts & Welding 16
Lecture 18

Foundations Structures
ARCH 331

Su2011abn

Framed Beam Connections

- angles
 - bolted
 - welded

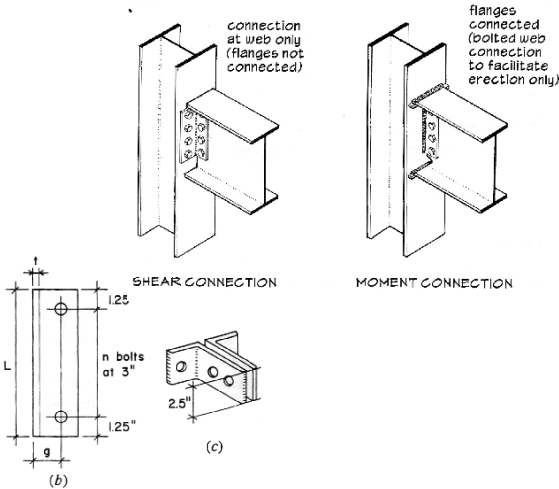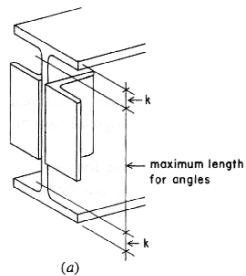

Steel Bolts & Welding 17
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Framed Beam Connections

- tables for standard bolt sizes & spacings
- # bolts
- bolt diameter, angle leg thickness
- bearing on beam web

Table 10-1 (continued)
All-Bolted Double-Angle Connections
3/4-in. Bolts

$F_y = 50$ ksi
 $F_u = 65$ ksi
 $F_y = 36$ ksi
 $F_u = 58$ ksi

4 Rows	Bolt Group	Thread Concl.	Bolt and Angle Available Strength, kips							
			Angle Thickness, in.							
			1/4	1/2	3/4	1	1 1/4	1 1/2		
W24, 21, 18, 16	N	STD	67.3	101	83.9	126	95.5	143	95.5	143
	X	STD	67.1	101	83.9	126	101	151	120	150
	SC	STD	50.8	75.9	50.8	75.9	50.8	75.9	50.8	75.9
	Class A	OWS	43.1	64.5	43.1	64.5	43.1	64.5	43.1	64.5
	Class B	SSLT	59.8	97.9	59.8	97.9	59.8	97.9	59.8	97.9
	SC	STD	67.1	101	83.9	126	84.4	127	84.4	127
	Class A	OWS	65.3	97.9	71.9	108	71.9	108	71.9	108
	Class B	SSLT	65.8	98.7	82.2	123	84.4	127	84.4	127
	N	STD	67.1	101	83.9	126	101	151	120	150
	X	STD	67.1	101	83.9	126	101	151	134	201
	SC	STD	63.3	94.9	63.3	94.9	63.3	94.9	63.3	94.9
	Class A	OWS	53.9	80.7	53.9	80.7	53.9	80.7	53.9	80.7
	Class B	SSLT	63.3	94.9	63.3	94.9	63.3	94.9	63.3	94.9
	SC	STD	67.3	101	83.9	126	101	151	108	156
	Class A	OWS	65.3	97.9	81.6	122	80.8	134	89.8	134
	Class B	SSLT	65.8	98.7	82.2	123	88.7	148	105	158

Beam Web Available Strength per Inch Thickness, kips/in.

Hole Type	STD		OWS		SSLT	
	ASD	LRFD	ASD	LRFD	ASD	LRFD
1/4 in.	187	250	175	262	156	234
1/2 in.	189	254	177	266	158	238
3/4 in.	171	237	160	230	141	204
1 in.	174	241	162	234	143	208
1 1/4 in.	171	237	160	230	141	204
1 1/2 in.	171	237	160	230	141	204

Support Available Strength per Inch Thickness, kips/in.

Hole Type	STD		OWS		SSLT	
	ASD	LRFD	ASD	LRFD	ASD	LRFD
1/4 in.	187	250	175	262	156	234
1/2 in.	189	254	177	266	158	238
3/4 in.	171	237	160	230	141	204
1 in.	174	241	162	234	143	208
1 1/4 in.	171	237	160	230	141	204
1 1/2 in.	171	237	160	230	141	204

Notes:
 STD = Standard holes
 OWS = Overlapped holes
 SSLT = Slit-labeled holes transverse to direction of load
 N = Threads included
 X = Threads excluded
 SC = Slip critical

Footnotes:
 * Tabulated values include 1/4-in. reduction in end distance, L_{eh} , to account for possible end-hole in beam length.
 Note: Slip-critical bolt values assume no more than one fillet has been provided or bolts have been welded to distribute loads in the flanges.


AMERICAN INSTITUTE OF STEEL CONSTRUCTION

Steel Bolts & Welding 19
Lecture 18

Foundations Structures
ARCH 331

Framed Beam Connections

- terms
 - coping

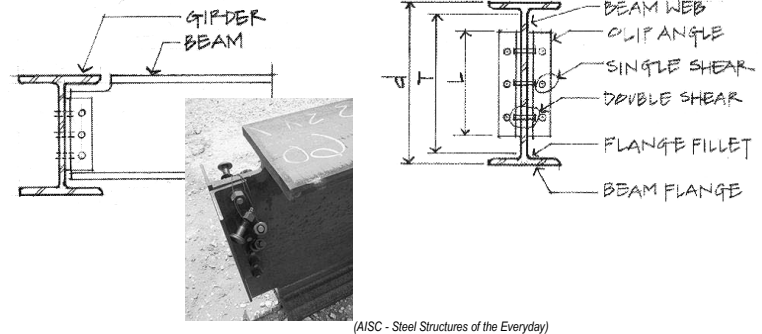

(AISC - Steel Structures of the Everyday)

Steel Bolts & Welding 18
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Framed Beam Connections

- welded example (shear)



(AISC - Steel Structures of the Everyday)


Steel Bolts & Welding 20
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Framed Beam Connections

- welded moment example

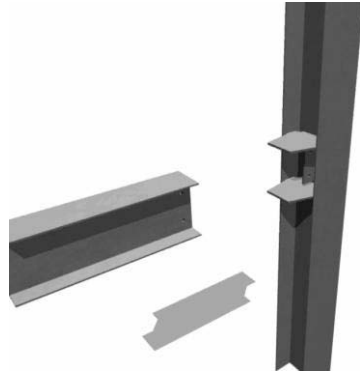

(AISC - Steel Structures of the Everyday)


Steel Bolts & Welding 21
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Framed Beam Connections

- welded/bolted moment example

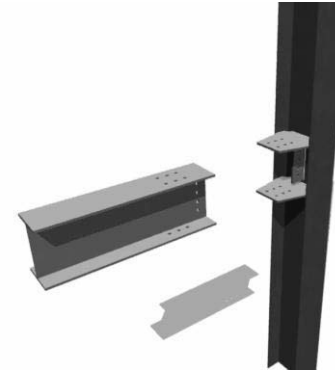

(AISC - Steel Structures of the Everyday)


Steel Bolts & Welding 22
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Framed Beam Connections

- welded/bolted moment example

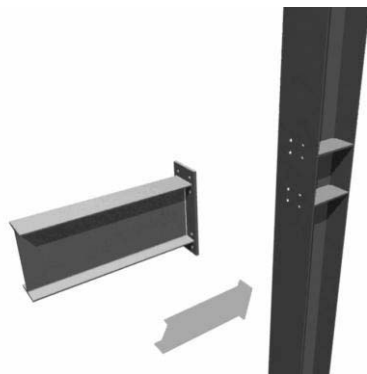

(AISC - Steel Structures of the Everyday)


Steel Bolts & Welding 23
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Beam Connections

- LRFD provisions
 - shear yielding
 - shear rupture
 - block shear rupture
 - tension yielding
 - tension rupture
 - local web buckling
 - lateral torsional buckling

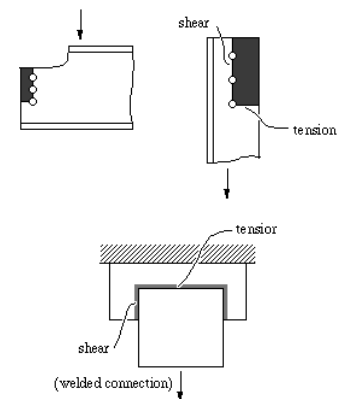

Steel Bolts & Welding 24
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Beam Connections

$$\phi = 0.75$$

$$R_n = 0.6F_u A_{nv} + U_{bs} F_u A_{nt} \leq 0.6F_y A_{gv} + U_{bs} F_u A_{nt}$$

– where U_{bs} is 1 for uniform tensile stress



Figure 2-1. Block Shear Rupture Limit State (Photo by J.A. Swanson and R. Leon, courtesy of Georgia Institute of Technology)

block shear rupture

Steel Bolts & Welding 25
Lecture 18



Figure 2-14. Tension Fracture Limit State (Photo by J.A. Swanson and R. Leon, courtesy of Georgia Institute of Technology)




tension rupture

Foundations Structures
ARCH 331

Su2011abn

Other Connections

- seated beam
- continuous
 - beam to column
 - beam to beam

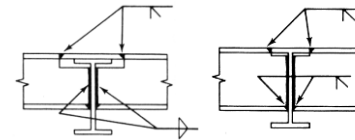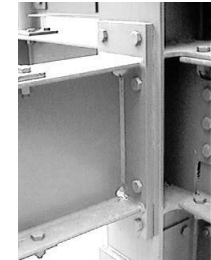


Steel Bolts & Welding 26
Lecture 21

Foundations Structures
ARCH 331

F2008abn

Other Connections


- splices

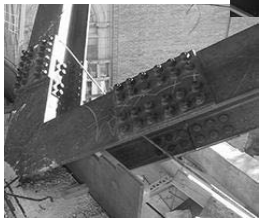

The Royal Ontario Museum Toronto, Canada
Daniel Libeskind
(AISC - Steel Structures of the Everyday)



Foundations Structures
ARCH 331

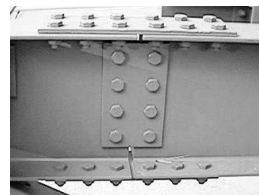

<http://courses.civil.ualberta.ca>
F2008abn

Steel Bolts & Welding 27
Lecture 21

Other Connections

- rigid frame knees
- gussets & joints



(AISC - Steel Structures of the Everyday)



Steel Bolts & Welding 28
Lecture 21

Foundations Structures
ARCH 331


F2008abn

- | Main Frame | Endwall Frame | Secondary |
|------------|-------------------|----------------|
| 1. Column | 3. Endwall column | 5. Wall girder |
| 2. Rafter | 4. Rake rafter | 6. Roof purlin |
| | | 7. Eave strut |




Other Connections


- *base plates*
 - *anchor bolts*
 - *bearing on steel*
 - *bending of plate*



<http://courses.civil.ualberta.ca>



Steel Bolts & Welding 29
Lecture 21

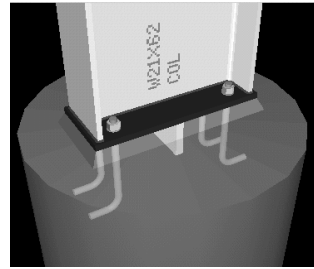

Foundations Structures
ARCH 331

F2008abn