ARCHITECTURAL STRUCTURES I:
STATICS AND STRENGTH OF MATERIALS
ENDS 231
DR. ANNE NICHOLS
SPRING 2007

lecture
twenty six

steel connections: bolts, welds & tension members

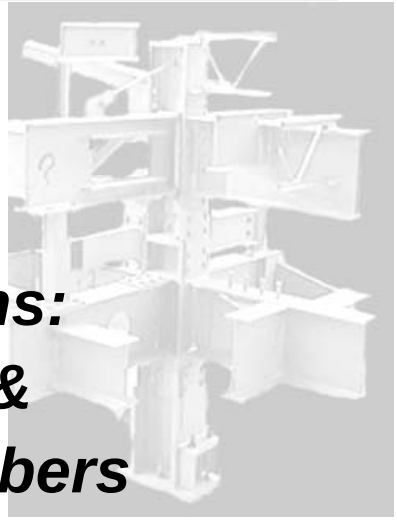

Connections

- needed to:
  - support beams by columns
  - connect truss members
  - splice beams or columns
- transfer load
- subjected to
  - tension or compression
  - shear
  - bending



(a) Framed beam (shear) connection.
e = Eccentricity; M = P × e



(b) Moment connection (rigid frame).
M = Moment due to beam bending

Bolts

- bolted steel connections

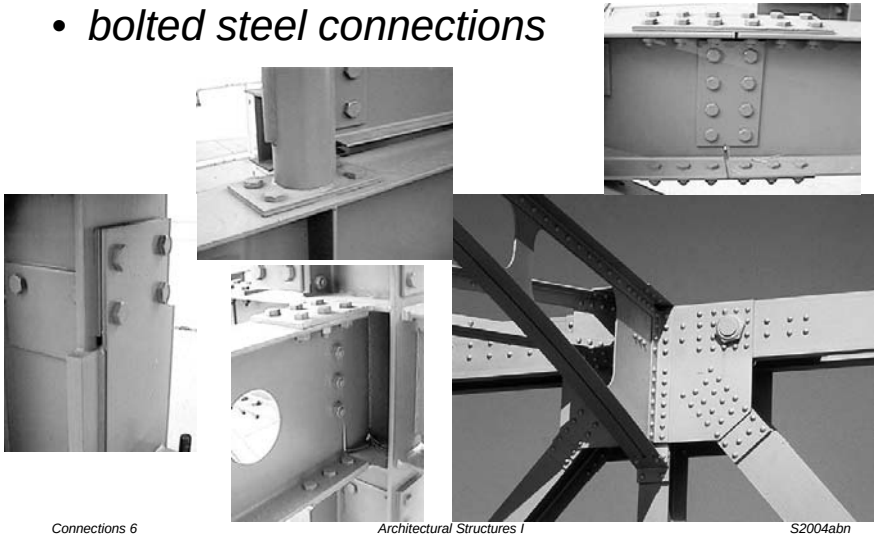

Welds

- welded steel connections

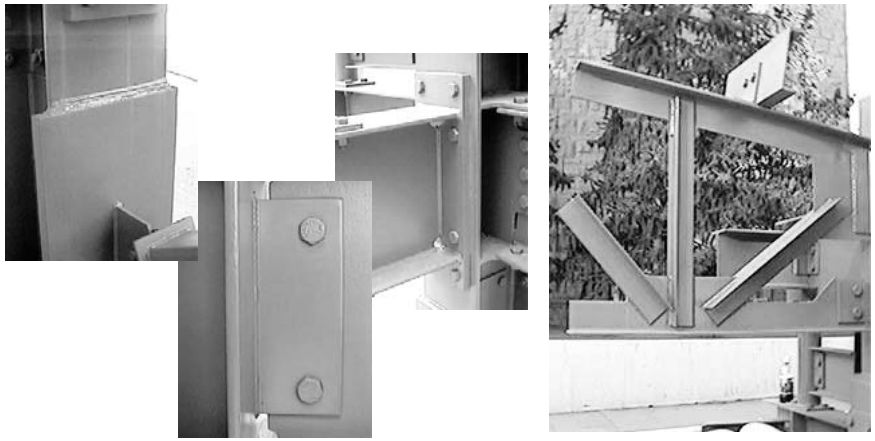

Fasteners

- *wood connections*

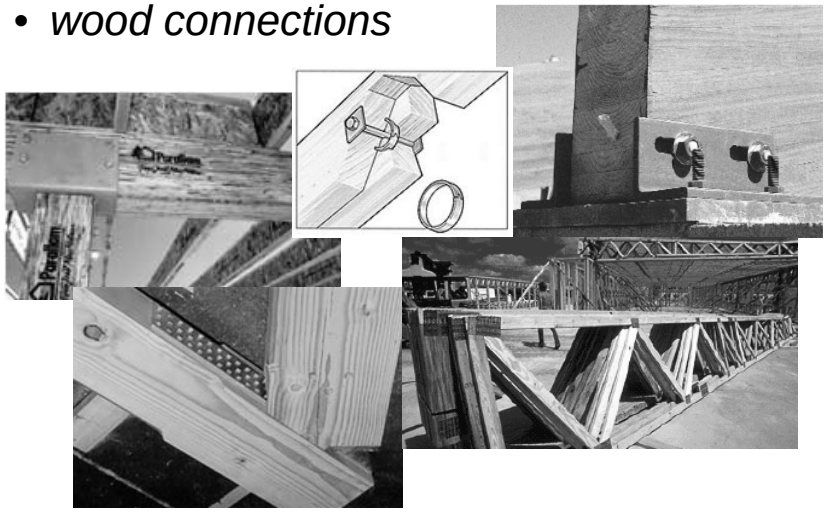

Bolted Connection Design

- *considerations*
  - *bearing stress*
    - *yielding*
  - *shear stress*
    - *single & double*
  - *member*
    - *rupture*

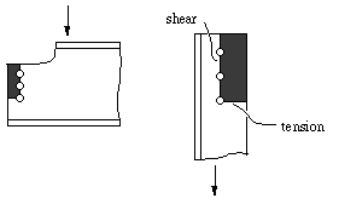

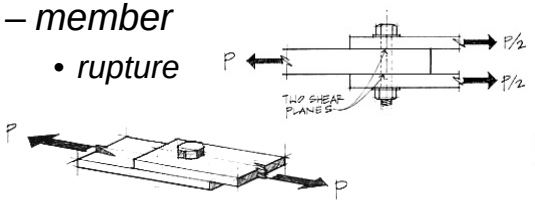

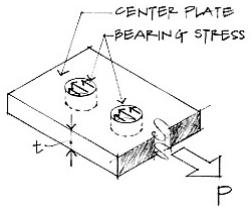

Bolted Connection Design

- *ASD steel*
  - *shear:*

$$f_v \le F_v$$

    - *bolt strengths*
    - *single & double*
  - *bolt types*
    - *A325-SC, A490-SC*
    - *A325-N, A490-N*
    - *A325-X, A490-X*

BOLTS, THREADED PARTS AND RIVETS
Shear
Allowable load in kips

TABLE SHEAR

	ASTM Designation	Connection Type[b]	Hole Type[b]	F_v, ksi	Load ing[c]	Nominal Diameter d, in.						
						⅝	¾	⅞	1	1⅛	1¼	1⅜	1½
						Area (Based on Nominal Diameter) in.[2]							
						.3068	.4418	.6013	.7854	.9940	1.227	1.485	1.767
Bolts	A307	—	STD NSL	10.0	S	3.1	4.4	6.0	7.9	9.9	12.3	14.8	17.7
					D	5.1	8.8	12.0	15.7	19.9	24.5	29.7	35.3
	A325	SC[a] Class A	STD	17.0	S	5.22	7.51	10.2	13.4	16.9	20.9	25.2	30.0
					D	10.4	15.0	20.4	26.7	33.8	41.7	50.5	60.1
			OVS, SSL	15.0	S	4.60	6.63	9.02	11.8	14.9	18.4	22.3	26.5
					D	9.20	13.3	18.0	23.6	29.8	36.8	44.6	53.0
			LSL	12.0	S	3.68	5.30	7.22	9.42	11.9	14.7	17.8	21.2
					D	7.36	10.6	14.4	18.8	23.9	29.4	35.6	42.4
		N	STD, NSL	21.0	S	6.4	9.2	12.6	16.5	20.9	25.8	31.2	37.1
					D	12.9	18.6	25.3	33.0	41.7	51.5	62.4	74.2
		X	STD, NSL	30.0	S	9.2	13.3	18.0	23.6	29.8	36.8	44.5	53.0
					D	18.4	26.5	36.1	47.1	59.8	73.6	89.1	106.0
	A490	SC[a] Class A	STD	21.0	S	6.44	9.26	12.6	16.5	20.9	25.8	31.2	37.1
					D	12.9	18.6	25.3	33.0	41.7	51.5	62.4	74.2
			OVS, SSL	18.0	S	5.52	7.95	10.8	14.1	17.9	22.1	26.7	31.8
					D	11.0	15.9	21.6	28.3	35.8	44.2	53.5	63.6
			LSL	15.0	S	4.60	6.63	9.02	11.8	14.9	18.4	22.3	26.5
					D	9.20	13.3	18.0	23.6	29.8	36.8	44.6	53.0
		N	STD, NSL	28.0	S	8.6	12.4	16.8	22.0	27.8	34.4	41.6	49.5
					D	17.2	24.7	33.7	44.0	55.7	69.7	83.2	99.0
		X	STD, NSL	40.0	S	12.3	17.7	24.1	31.4	39.8	49.1	59.4	70.7
					D	24.5	35.3	48.1	62.8	79.6	98.2	119.0	141.0
Rivets	A502-1	—	STD	17.5	S	5.4	7.7	10.5	13.7	17.4	21.5	26.0	30.9
					D	10.7	15.5	21.0	27.5	34.8	42.9	52.0	61.8
	A502-2 A502-3	—	STD	22.0	S	6.7	9.7	13.2	17.3	21.9	27.0	32.7	38.9
					D	13.5	19.4	26.5	34.6	43.7	54.0	65.3	77.7
	A36 (F_u=58 ksi)	N	STD	9.9	S	3.0	4.4	6.0	7.8	9.8	12.1	14.7	17.5
					D	6.1	8.7	11.9	15.6	19.7	24.3	29.4	35.0
		X	STD	12.8	S	3.9	5.7	7.7	10.1	12.7	15.7	19.0	22.6

Bolted Connection Design

- *ASD steel*
  - *bearing:*
    - *bolts rarely fail by bearing*
    - *other part fails first*

BOLTS AND THREADED PARTS
Bearing
Allowable loads in kips

TABLE BEARING
Slip-critical and Bearing-type Connections

Material Thickness	F_u = 58 ksi Bolt dia.			F_u = 65 ksi Bolt dia.			F_u = 70 ksi Bolt dia.			F_u = 100 ksi Bolt dia.		
	¾	⅞	1	¾	⅞	1	¾	⅞	1	¾	⅞	1
⅛	6.5	7.6	8.7	7.3	8.5	9.6	7.9	9.2	10.5	11.3	13.1	15.0
3/16	9.8	11.4	13.1	11.0	12.8	14.6	11.8	13.8	15.6	16.9	19.7	22.5
¼	13.1	15.2	17.4	14.6	17.1	19.5	15.8	18.4	21.0	22.6	26.3	30.0
5/16	16.3	19.0	21.8	18.3	21.3	24.4	19.7	23.0	26.3	28.1	32.8	37.5
⅜	19.5	22.8	26.1	21.9	25.6	29.3	23.6	27.6	31.5	33.8	39.4	45.0
7/16	22.8	26.6	30.5	25.6	29.9	34.1	27.6	32.2	36.8		45.9	52.5
½	26.1	30.5	34.8	29.3	34.1	39.0	31.5	36.8	42.0			60.0
9/16	29.4	34.3	39.2	32.9	38.4	43.9		41.3	47.3			
⅝	32.6	38.1	43.5		42.7	48.8		45.9	52.5			
11/16		41.9	47.9		46.9	53.6			57.8			
¾		45.7	52.2			58.5						
13/16			56.6									
⅞			60.9									
15/16												
1	52.2	60.9	69.6	58.5	68.3	78.0	63.0	73.5	84.0	90.0	105.0	120.0

Tension Members

- *steel members can have <u>holes</u>*
- *reduced area*
- *increased stress*

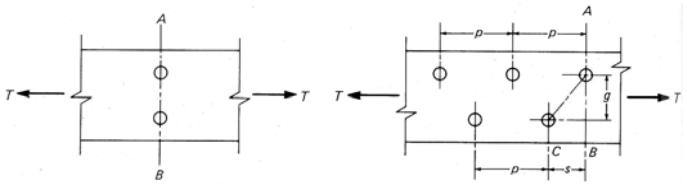

Effective Net Area

- *likely path to "rip" across*
- *bolts divide transferred force too*

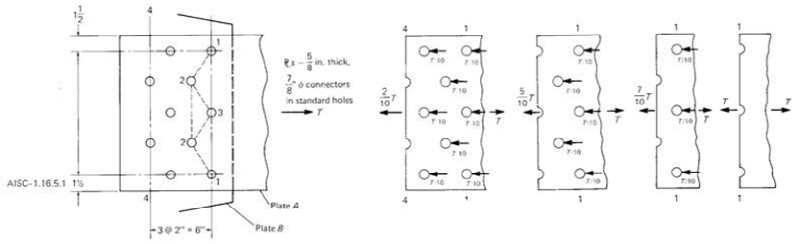

ASD – Tension Members

- non-pin connected members:
  - $F_t = 0.60F_y$ *on gross area*
  - $F_t = 0.50F_u$ *on net area*
- pin connected members:
  - $F_t = 0.45F_y$ *on net area*
- threaded rods of approved steel:
  - $F_t = 0.33F_u$ *on major diameter*
  - *(for static loading only)*

LRFD - Tension Members

- *limit states for failure* $P_u \le \phi_t P_n$

1. *yielding* $\phi_t = 0.9 \quad P_n = F_y A_g$
2. *rupture** $\phi_t = 0.75 \quad P_n = F_u A_e$

A_g - *gross area*
A_e - *effective net area*
F_u - *tensile strength of the steel (ultimate)*

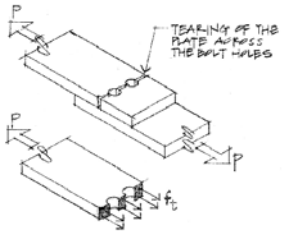

Welded Connection Design

- *considerations*
  - *shear stress*
  - *yielding*
  - *rupture*



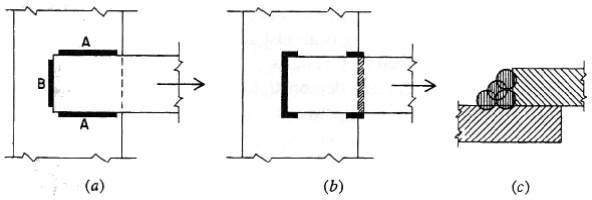

Welded Connection Design

- *weld terms*
  - *butt weld*
  - *fillet weld*
  - *plug weld*
  - *throat*
- *weld materials*
  - *E60XX*
  - *E70XX*
    F_{EXX} = 70 ksi





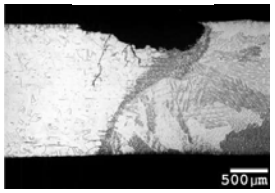

TABLE J2.4
Minimum Size of Fillet Welds

Material Thickness of Thicker Part Joined, in. (mm)	Minimum Size of Fillet Weld[a] in. (mm)
To ¼ (6) inclusive	⅛ (3)
Over ¼ (6) to ½ (13)	3/16 (5)
Over ½ (13) to ¾ (19)	¼ (6)
Over ¾ (19)	5/16 (8)

[a] Leg dimension of fillet welds. Single pass welds must be used.
[b] See Section J2.2b for maximum size of fillet welds.

Welded Connection Design

- *ASD*
  - *shear* $f_v \le F_v$
    - $F_v = 0.30F_{weld}$
  - *throat*
    - *T =0.707 x weld size*
  - *area*
    - *A = T x length of weld*
  - *weld metal generally stronger than base metal (ex. F_y = 50 ksi)*

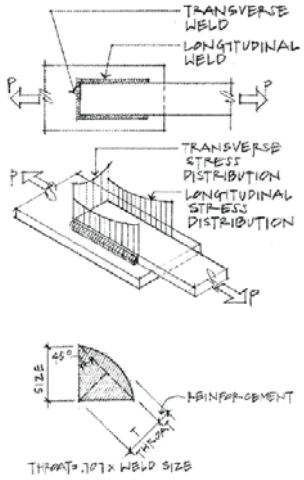

Framed Beam Connections

- *angles*
  - *bolted*
  - *welded*

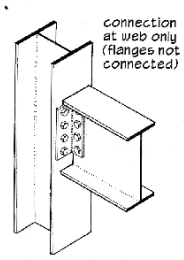

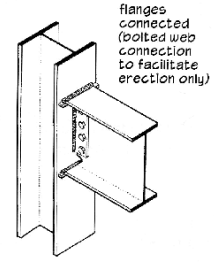

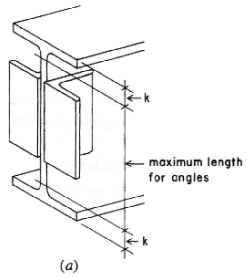

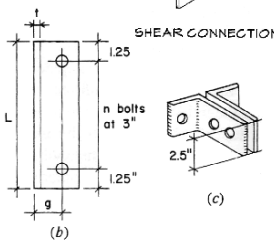

Framed Beam Connections

- *terms*
  - *coping*

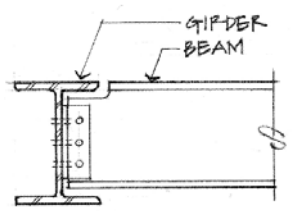

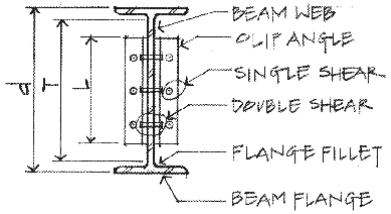

Framed Beam Connections

- *tables for standard bolt holes & spacings*
- *n = # bolts*
- *angle leg thickness*
- *length needed*

FRAMED BEAM CONNECTIONS
Bolted
TABLE Allowable loads in kips

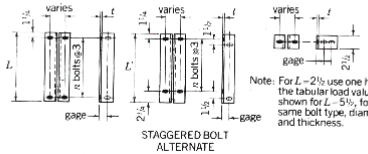

Note: For $L - 2\frac{1}{2}$ use one half the tabular load value shown for $L - 5\frac{1}{2}$, for the same bolt type, diameter, and thickness.

TABLE Bolt Shear[a]
For bolts in **bearing-type** connections with standard or slotted holes.

Bolt Type			A325-N			A490-N			A325-X			A490-X		
F_v, Ksi			21.0			28.0			30.0			40.0		
Bolt Dia., d In.			¾	⅞	1	¾	⅞	1	¾	⅞	1	¾	⅞	1
Angle Thickness t, In.			9/16	⅜	⅝	⅜	½	⅝	⅜	⅝	⅝	½	⅝	⅝
L In.	L' In.	n												
29½	31	10	186	253	330	247	337	440[b]	265	361	[c]	353	481	[c]
26½	28	9	167	227	297	223	303	396[b]	239	325	[c]	318	433	[c]
23½	25	8	148	202	264	198	269	352[b]	212	289	[c]	283	385	[c]
20½	22	7	130	177	231	173	236	308[b]	186	253	[c]	247	337	[c]
17½	19	6	111	152	196	148	202	264[b]	159	216	283	212	289	377
14½	16	5	92.8	126	165	124	168	220[b]	133	180	236	177	242	314
11½	13	4	74.2	101	132	99.0	135	176[b]	106	144	188	141	192	251

Beam Connections

- *LRFD provisions*
  - *shear yielding*
  - *shear rupture*
  - *block shear rupture*
  - *tension yielding*
  - *tension rupture*
  - *local web buckling*
  - *lateral torsional buckling*

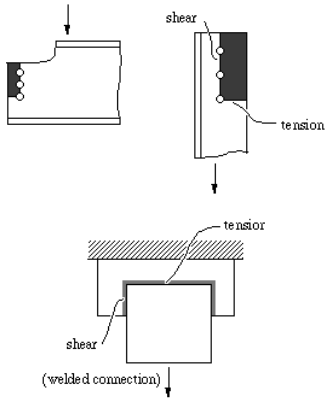

Beam Connections

- *block shear rupture*
- *tension rupture*

Figure 2-13 Block Shear Rupture Limit State (Photo by J.A. Swanson and R. Leon, courtesy of Georgia Institute of Technology)

Figure 2-14 Tension Fracture Limit State (Photo by J.A. Swanson and R. Leon, courtesy of Georgia Institute of Technology)